



DOI:10.29013/AJT-25-3.4-54-58



## RATIONAL USE OF SPENT CATALYSTS AS A SOURCE OF MICRO- AND MACROELEMENTS FOR LIQUID FERTILIZERS

**Obidzhonov Doniyorjon Orip ogli <sup>1</sup>, Kucharov Bakhrom Xayriyevich <sup>1</sup>,  
Erkaev Aktam Ulashevich <sup>2</sup>, Zakirov Bakhtiyor Sabirjanoich <sup>1</sup>,  
Yulbarsova Mashkhurakhon Vahobovna <sup>1</sup>**

<sup>1</sup> Institute of General and Inorganic Chemistry of the Academy  
of Sciences of the Republic of Uzbekistan

<sup>2</sup> Tashkent Institute of Chemical Technology

---

**Cite:** Obidzhonov D.O., Kucharov B.X., Erkaev A.U., Zakirov B.S., Yulbarsova M.V. (2025). Rational use of Spent Catalysts as a Source of Micro- and Macroelements for Liquid Fertilizers. *Austrian Journal of Technical and Natural Sciences* 2025, No 3–4. <https://doi.org/10.29013/AJT-25-3.4-54-58>

---

### Abstract

This article discusses the possibilities of obtaining water-soluble liquid fertilizers enriched with microelements by acid processing of spent catalysts of the SHIFT MAX 210 brand, widely used in the nitrogen industry. Studies have been conducted on the effect of nitric acid concentration (in the range of 20–50%) on the degree of extraction of macro- and microelements. Physicochemical and rheological properties of the obtained solutions have been determined. The results demonstrate the prospects for developing an energy-efficient technology for processing catalyst waste using local raw materials, which is relevant in the environmental conditions of the Republic of Uzbekistan.

**Keywords:** microelements, system, catalyst, Shift max 210, liquid fertilizers, nitric acid, processing

### Introduction

At present, the problem of organizing the production of water-soluble complex fertilizers remains unresolved in Uzbekistan, since technologies for their production from local raw materials have not yet been developed in the conditions of the republic. In this regard, the creation of our own production of such fertilizers is a relevant and promising task.

One of the key objectives of the study is to determine the role of soil-forming processes,

identify the deficiency or excess of microelements and develop recommendations for the effective use of micronutrients. Also, based on the data obtained, it will be possible to adjust micronutrient maps for planning fertilizers and conducting further research in agriculture.

Copper is found in all organs and all phases of cotton growing, when growing it on different soils. Copper microfertilizers for cotton are used with sufficient provision

of the optimal amount of basic fertilizers (N, P, K), in areas where the content of copper available to plants in the arable horizon is less than 0.6 mg / kg of soil (Chernavina I. A., 1970; Shkolnik M.Ya., Davydova V. N., 1962; Klimovitskaya Z. M., 1964).

The role of zinc in the ontogenesis of cotton in the conditions of irrigated agriculture in Central Asia has not been sufficiently elucidated (Rinkis G.Ya. 1972; Yakovleva V. V., Sobachkina L. N. 1972; Yakovleva V. V., Sobachkina L. N. 1972; Vinogradova H. T. 1952; Enileev H. H., Andrishchenko V. K. 1963; Pirahunov T. P. 1966). The forms and types of zinc bonds in a living organism are varied.

Manganese influences the course of oxidation-reduction reactions in plants: in ammonia, plants behave as an oxidizer, and in nitrate, as a reducing agent.

The physiological role of molybdenum in plants is associated with its participation in dense metabolism, primarily in enzymatic reduction to ammonia and in the synthesis of proteins and amino acids (Zhmai L. A., 2004).

In recent years, data have been obtained on the positive effect of molybdenum on phosphorus metabolism in plants (Zavalin A. A., Almetov N. S. 2006; Mineev V. G., 2006). The introduction of molybdenum not only sharply increases the amount of organic phosphorus, but also leads to a qualitative change in protein.

In order to provide a physicochemical justification for the process of obtaining microelements, the physicochemical characteristics of spent catalysts used in the nitrogen industry, the accumulation volumes of which reach hundreds of tons, were studied before the stage of decomposition with mineral acids. The energy dispersive spectra of these catalysts are shown in Figure 1. Before use, the catalysts were crushed to a particle size of less than 0.05 mm.

### Methods and materials

To obtain liquid microelement-containing fertilizers, solutions were used that were obtained by nitric acid decomposition of spent catalysts formed during the production of the nitrogen industry.

The process of acid processing of catalysts was carried out as follows: in laboratory

conditions, nitric acid solutions with concentrations of 20%, 30%, 40% and 50% were used to process 10 g of catalyst waste (SHIFT MAX 210 brand).

The process of decomposition of the crushed catalyst (to a particle size of 0.05 mm) was carried out on a laboratory set-up consisting of a tubular glass reactor with a stirrer equipped with an electric wire and placed in a water thermostat. The temperature in the thermostat was maintained using a TK-300I thermometer and an RT-230U electronic relay and was constant, amounting to 45 °C. The rotation speed of the stirrer was regulated within 250–300 rpm.

The interaction process of the components lasted for 30 minutes. Upon completion of the decomposition, the reaction mass was separated into liquid and solid phases by filtration. The reactor contents were filtered through a Buchner funnel using a Bunsen flask, under a vacuum of 0.60 mm Hg and one layer of “white ribbon” filter paper. The filters were pre-weighed. The sediment remaining on the filter was washed with 10 g of water at a given temperature and dried with the filter at 100 °C until a constant weight was achieved.


### Results and discussion

A comparative analysis of the results of energy-dispersive spectral research of spent catalysts showed that their elemental composition has a significant diversity. For example, in the catalyst of the SHIFT MAX 210 brand, the copper and zinc content is 2.52% and 2.47%, respectively (Table 1).

The results of mass spectrometric analysis (ICP-MS) presented in Table 3 also confirm that the spent catalysts contain a wide range of macro- and microelements that are necessary for the production of liquid complex fertilizers with microelements.

After decomposition with nitric acid, the liquid phase was analyzed for elemental composition, which is given in Table 2. As follows from Table 2, the liquid phase has in its composition and contains: P-242.0, K-478.0, Ca-1207, Mg-580 mcg/l macroelements and B-50.0, **Cu**-28000, **Zn**-19100, Co-68.0, Mn-214 and Fe-545605 mcg/l microelements, respectively.

**Figure 1.** Energy dispersive spectrum of the spent initial catalyst of the SHIFT MAX 210 brand

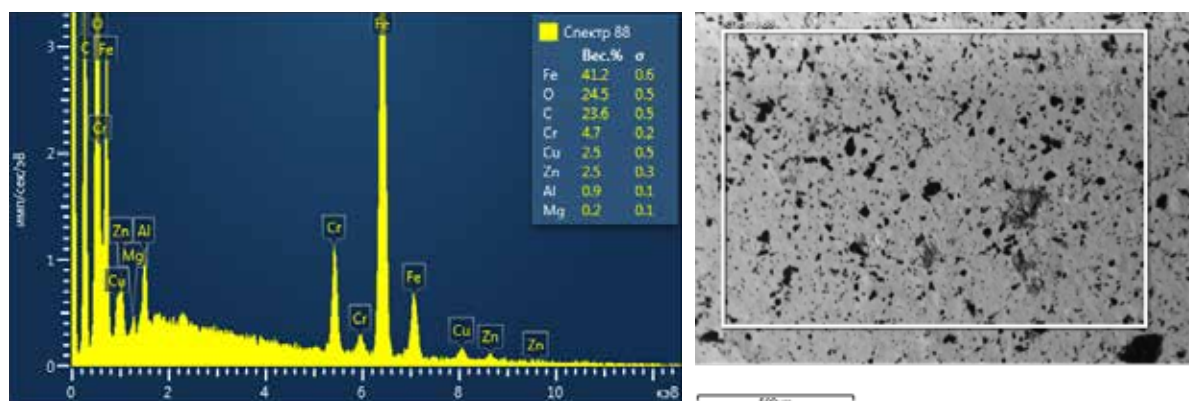

**Table 1.** Elemental composition of the spent initial catalyst brand SHIFT MAX210

Element	Weight. %	Sigma Weight %	Name of the standard
C	23.58	0.53	With Vit
O	24.47	0.46	SiO <sub>2</sub>
Mg	0.25	0.08	MgO
Al	0.87	0.09	Al <sub>2</sub> O <sub>3</sub>
Cr	4.69	0.21	Cr
Fe	41.15	0.57	Fe
Cu	2.52	0.48	Cu
Zn	2.47	0.35	Zn
Sum:	100.00		

**Table 2.** Mass spectrometric (ICP-MS) analysis of the initial spent catalysts

Brand of catalysts	Macroelements, mcg/l					Microelements, mcg/l					
	P	K	Ca	Mg	Cu	Zn	B	Mn	Fe	Co	Mo
Shift max 210	242.0	478.0	1207	580	28000	19100	50.0	4300	545605	68.0	214

We then investigated the influence of process parameters on the process of nitric acid decomposition of catalyst waste (Table 3).

**Table 3.** Study of the influence of technological parameters on the process of nitric acid decomposition of catalyst waste

No.	Ratio Cat: HNO <sub>3</sub>	Concentra- tion HNO <sub>3</sub> ,%	Filtration rate, kg/m <sup>2</sup> * h		W: T ratio	Humidity, %
			main fil- trate	wash fil- trate		
Waste catalyst brand SHIFT MAX 210						
1	1:10	20	457.08	47.12	12.18:1.0	29.11
2	1:10	30	378.70	69,70	11.62:1.0	26.64
3	1:10	40	305.45	57.44	12.20:1.0	27.63
4	1:10	50	128.5	69.50	10.62:1.0	28.74

**Table 4.** Mass spectrometric (ICP-MS) analysis liquid phase of SHIFT  
MAX 210 catalyst after decomposition with nitric acid

acid concentration, %	Macroelements, mcg/l					Microelements, mcg/l						
	P	K	Ca	Mg	Cu	Zn	B	Mn	Fe	Co	Mo	
20	1200	94000	320000	53000	2600	2100	56.0	55000	280000	4900	720	
30	1300	60000	290000	54000	2900	2300	53.0	66000	350000	6300	530	
40	1400	46000	260000	49000	2900	2300	43.0	69000	390000	4900	400	
50	1400	58000	270000	49000	3100	2500	38.0	72000	400000	5500	420	

The table presents the results of the analysis of the macro- and microelement composition of solutions obtained by decomposing nitrogen industry catalysts with nitric acid of different concentrations (20%, 30%, 40%, 50%). (Table 4)

Increasing the concentration of nitric acid contributes to:

- Increasing the content of phosphorus, iron, manganese and some other elements in the solution;
- At the same time, the solubility of potassium, calcium, boron and molybdenum deteriorates.

At a certain concentration of acid (approximately 40–50%), the process of release of many elements stabilizes, or their content changes insignificantly.

**Table 5.** Rheological properties of the obtained solutions of Shift  
max 210 catalysts after ammonization before filtration at

No.	Density before filtration, g/cm <sup>3</sup>				Viscosity before filtration, mm <sup>2</sup> /s				pH
	Temperature °C								
	10	20	30	45	10	20	30	45	
1	1.21596	1.21227	1.20545	1.19859	1.7167	1.4503	1.2727	1.2283	2.11
2	1.19318	1.18624	1.18182	1.17694	2.5455	2.2199	2.0127	1.8351	4.69
3	1.20563	1.20005	1.19563	1.18905	2.2791	2.0127	1.7759	1.6575	6.01
4	1.19800	1.19440	1.18699	1.18485	2.4271	2.3087	2.0719	1.9535	7.45

Studies have shown that with an increase in the temperature of the medium from 10 to 45 °C, the density and viscosity of the solution decrease in direct proportion, i.e. 1.19800–1.18485 g/cm<sup>3</sup> and 2.4271–1.9535 mm<sup>2</sup>/s, respectively. (Table 5)

### Conclusion

As a result of the conducted research, it was established that spent catalysts of the nitrogen industry of the SHIFT MAX 210 brand are a valuable source of macro- and microelements necessary for the production of liquid complex fertilizers.

The conducted studies have shown that the spent catalysts SHIFT MAX 210 contain a large number of useful elements (iron, cop-

per, zinc, etc.), which can be used to obtain liquid fertilizers.

Decomposition of catalysts with nitric acid of different concentrations (20–50%) revealed that with increasing acid concentration, the content of phosphorus, iron and manganese in the solution increases, but the solubility of potassium, calcium, boron and molybdenum decreases; at an acid concentration of 40–50%, the composition of the solutions stabilizes. Rheological studies showed that with an increase in temperature from 10 to 45 °C, the density and viscosity of the solutions decrease, which improves the filtration conditions.

## References

- Chernavina I. A. Physiology and biochemistry of microelements. Moscow: Higher School, 1970. – 310 p.
- Shkolnik M. Ya., Davydova V. N. On partial elimination of zinc deficiency in plants using vitamins B1 and B6 – “DAN SSSR”, 1962. – No. 1.
- Klimovitskaya Z. M. On the physiological significance of manganese for plant growth and development. Abstract of doctoral diss., – Kyiv, 1964.
- Rinkis G. Ya. Molybdenum supply to plants depending on the amount of other elements in the nutrient substrate. In the book “Biological role of molybdenum”, – Moscow, 1972.
- Yakovleva V. V., Sobachkina L. N. Effect of molybdenum on phosphorus metabolism in plants. In: “Biological role of molybdenum” – Moscow, “Nauka” Publishing House, 1972.
- Vinogradova H. T. Molybdenum and its biological role. In the collection “Microelements in the life of plants and animals”. – Moscow, Publishing House of the USSR Academy of Sciences, 1952.
- Enileev H. H., Andrishchenko V. K. On the influence of microelements on protein metabolism in germinating cotton seeds. “Uzb. biol. journal”. 1963. – No. 4.
- Pirahunov T. P. The Importance of Molybdenum in Increasing the Use of Soil Nitrogen and Fertilizers by Cotton. Abstracts of Reports at the All-Union Conference on Microelements, – Irkutsk, 1966.
- Zhmai L. A. Ammonium nitrate in Russia and in the world // Scientific and technical news. – Moscow, 2004. Special issue. – No. 2. – P. 23–24.
- Zavalin A. A., Almetov N. S. Effect of nitrogen fertilizer and biopreparations on the yield and grain quality of winter wheat on sod-weakly podzolic light loamy soil // Journal of Agrochemistry. – No. 6. 2006. – 38 p.
- Mineev V. G., Journal of Agrochemistry, Science 2006. – 526 p.

submitted 16.04.2025;

accepted for publication 30.04.2025;

published 29.05.2025

© Obidzhonov D. O., Kucharov B. X., Erkaev A. U., Zakirov B. S., Yulbarsova M. V.

Contact: doniyor\_obidjonov94@mail.ru